



**INSTYTUT TECHNIKI BUDOWLANEJ**  
PL 00-611 WARSZAWA  
ul. Filtrowa 1  
tel.: (+48 22) 825-04-71  
(+48 22) 825-76-55  
fax: (+48 22) 825-52-86  
[www.itb.pl](http://www.itb.pl)



Member of



[www.eota.eu](http://www.eota.eu)

## European Technical Assessment

**ETA-09/0140  
of 17/05/2019**

### General Part

**Technical Assessment Body issuing the European Technical Assessment**

Instytut Techniki Budowlanej

**Trade name of the construction product**

BOSSONG BCR V PLUS, BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T

**Product family to which the construction product belongs**

Bonded fasteners for use in concrete

**Manufacturer**

BOSSONG S.p.A.  
Via Enrico Fermi, 49/51,  
IT-24050 Grassobbio (Bg), Italy  
[www.bossong.com](http://www.bossong.com)

**Manufacturing plant**

BOSSONG S.p.A.  
Via Enrico Fermi, 49/51,  
IT-24050 Grassobbio (Bg), Italy

**This European Technical Assessment contains**

29 pages including 3 Annexes which form an integral part of this assessment

**This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of**

European Assessment Document EAD 330499-01-0601 „Bonded fasteners for use in concrete”

**This version replaces**

ETA-09/0140 issued on 25/02/2014

*This European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and should be identified as such.*

*Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may be made, with the written consent of the issuing Technical Assessment Body. Any partial reproduction has to be identified as such.*

## Specific Part

### 1 Technical description of the product

The BOSSONG BCR V PLUS, BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T are bonded fasteners (injection type) consisting of an injection mortar cartridge using an applicator gun equipped with a special mixing nozzle and steel element: commercial threaded rod of the sizes M8 to M30 with hexagon nut and washer or reinforcing bar (rebar) from Ø8 to Ø32 mm.

The steel element is placed into a drilled hole previously injected (using an applicator gun) with a mortar with a slow and slight twisting motion. The steel element is anchored by the bond between steel element, mortar and concrete.

An illustration and the description of the products are given in Annex A.

### 2 Specification of the intended use in accordance with the applicable European Assessment Document (EAD)

The performances given in clause 3 are only valid if the anchors are used in compliance with the specifications and conditions given in Annex B.

The performances given in this European Technical Assessment are based on an assumed working life of the anchor of 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

### 3 Performance of the product and references to the methods used for its assessment

#### 3.1 Performance of the product

##### 3.1.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic  | Performance        |
|---|--------------------|
| Characteristic resistance to tension load and shear load (static and quasi static loading), displacements | See Annex C1 to C7 |
| Characteristic resistance for seismic performance category C1   | See Annex C8       |
| Characteristic resistance for seismic performance category C2   | See Annex C9       |

##### 3.1.2 Hygiene, health and the environment (BWR 3)

No performance assessed.

#### 3.2 Methods used for the assessment

The assessment of the product has been made in accordance with the EAD 330499-01-0601 „Bonded fasteners for use in concrete”.

**4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base**


According to Decision 96/582/EC of the European Commission the system 1 of assessment and verification of constancy of performance (see Annex V to Regulation (EU) No 305/2011) applies.

**5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document (EAD)**


Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Instytut Techniki Budowlanej.

For type testing the results of the tests performed as part of the assessment for the European Technical Assessment shall be used unless there are changes in the production line or plant. In such cases the necessary type testing has to be agreed between Instytut Techniki Budowlanej and the notified body.

Issued in Warsaw on 17/05/2019 by Instytut Techniki Budowlanej

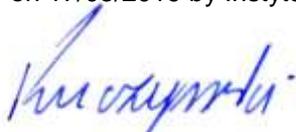

Krzysztof Kuczeński, PhD  
Deputy Director of ITB

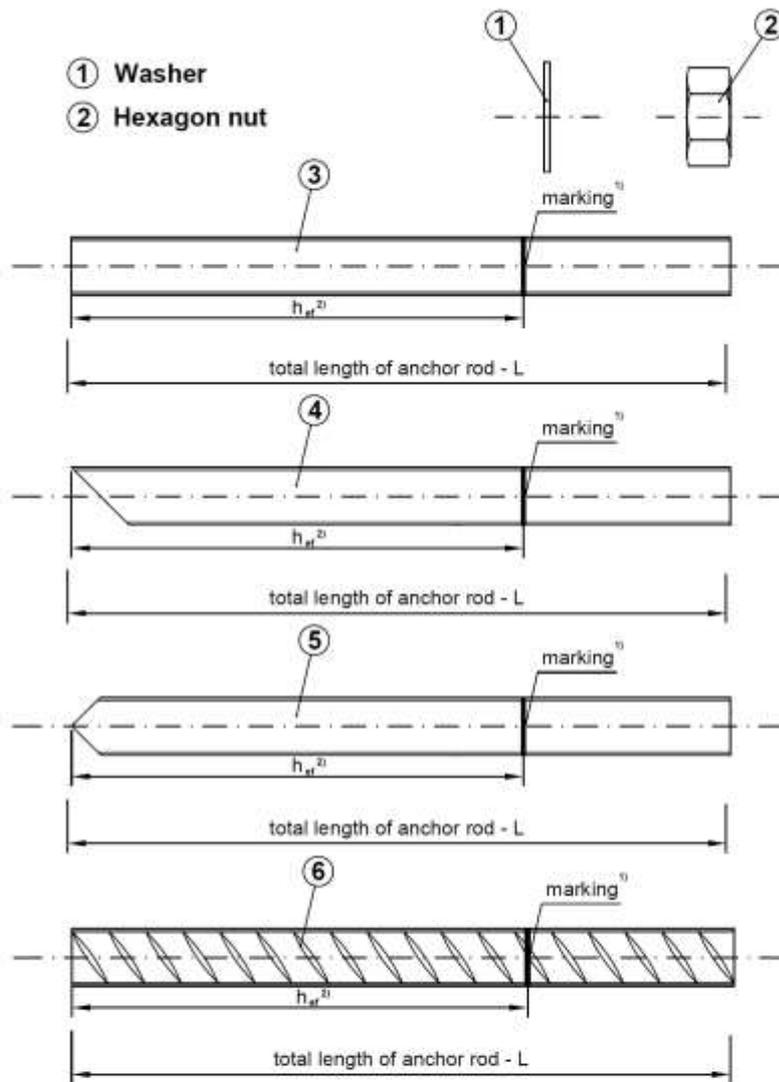

<sup>1)</sup> Marking according to clause 1.1 of EAD 330499-01-0601

<sup>2)</sup> Effective anchorage depth according to Table B1 and B2 (Annex B2 and B3)

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Product description**  
Steel elements

**Annex A1**  
of European  
Technical Assessment  
ETA-09/0140

| <b>Table A1: Threaded rods</b>  |   |   |  |                            |   |
|---|---|---|--|----------------------------|---|
| <b>Designation</b>  |   | <b>Material</b>                               |  |                            |   |
| <b>Steel, zinc plated</b>   |   |   |  |                            |   |
| <b>electroplated <math>\geq 5 \mu\text{m}</math> acc. to EN ISO 4042</b>  |   |   |  |                            |   |
| <b>hot-dip galvanized <math>\geq 40 \mu\text{m}</math> acc. to EN ISO 1461</b>  |   |   |  |                            |   |
| Threaded rod  | <b>Property class</b>   | <b>Characteristic steel ultimate strength</b> | <b>Characteristic steel yield strength</b> | <b>Fracture elongation</b> | EN ISO 898-1  |
|   | 4.8   | $f_{uk} \geq 400 \text{ N/mm}^2$              | $f_{yk} \geq 320 \text{ N/mm}^2$           | $A_5 > 8\%^{1)}$           |   |
|   | 5.8   | $f_{uk} \geq 500 \text{ N/mm}^2$              | $f_{yk} \geq 400 \text{ N/mm}^2$           | $A_5 > 8\%^{1)}$           |   |
|   | 8.8   | $f_{uk} \geq 800 \text{ N/mm}^2$              | $f_{yk} \geq 640 \text{ N/mm}^2$           | $A_5 \geq 12\%^{1)}$       |   |
|   | 10.9  | $f_{uk} \geq 1000 \text{ N/mm}^2$             | $f_{yk} \geq 900 \text{ N/mm}^2$           | $A_5 > 9\%^{1)}$           |   |
| Hexagon nut   | 4   | for class 4.8 rods                            |  |                            | EN 898-2  |
|   | 5   | for class 5.8 rods                            |  |                            |   |
|   | 8   | for class 8.8 rods                            |  |                            |   |
|   | 10  | for class 10.9 rods                           |  |                            |   |
| Washer  | Steel, according to EN ISO 7089; corresponding to anchor rod material |   |  |                            |   |
| <b>Stainless steel A2 (Materials) 1.4301, 1.4307, 1.4567, 1.4541</b>  |   |   |  |                            |   |
| <b>Stainless steel A4 (Materials) 1.4401, 1.4404, 1.4571, 1.4362, 1.4578</b>  |   |   |  |                            |   |
| <b>High corrosion resistance stainless steel (HCR) (Materials) 1.4529, 1.4565</b>   |   |   |  |                            |   |
| Threaded rod  | <b>Property class</b>   | <b>Characteristic steel ultimate strength</b> | <b>Characteristic steel yield strength</b> | <b>Fracture elongation</b> | EN 10088<br>EN ISO 3506   |
|   | 50  | $f_{uk} \geq 500 \text{ N/mm}^2$              | $f_{yk} \geq 210 \text{ N/mm}^2$           | $A_5 > 8\%^{1)}$           |   |
|   | 70  | $f_{uk} \geq 700 \text{ N/mm}^2$              | $f_{yk} \geq 450 \text{ N/mm}^2$           | $A_5 \geq 12\%^{1)}$       |   |
|   | 80  | $f_{uk} \geq 800 \text{ N/mm}^2$              | $f_{yk} \geq 600 \text{ N/mm}^2$           | $A_5 \geq 12\%^{1)}$       |   |
| Hexagon nut   | 50  | for class 50 rods                             |  |                            | EN 10088<br>EN ISO 3506   |
|   | 70  | for class 70 rods                             |  |                            |   |
|   | 80  | for class 80 rods                             |  |                            |   |
| Washer  | Steel, according to EN 10088; corresponding to anchor rod material    |   |  |                            |   |
| <sup>1)</sup> For seismic performance category C1 and C2, $A_5 > 19\%$  |   |   |  |                            |   |
| Commercial standard threaded rods may be used, with:  |   |   |  |                            |   |
| – material and mechanical properties according to Table A3,   |   |   |  |                            |   |
| – confirmation of material and mechanical properties by inspection certificate 3.1 according to EN-10204:2004,                          |   |   |  |                            |   |
| – marking of the threaded rod with the embedment depth.   |   |   |  |                            |   |
| Note: Commercial standard threaded rods made of galvanized steel with property class above 8.8 are not permitted in some Member States. |   |   |  |                            |   |
| <b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b>  |   |   |  |                            | <b>Annex A2</b><br>of European<br>Technical Assessment<br>ETA-09/0140 |
| <b>Product description</b><br>Materials (1)   |   |   |  |                            |   |

**Table A2: Reinforcing bars (Rebar)**

| Designation                                 | Material   |
|---|--|
| Rebar according to EN 1992-1-1:2004+AC:2010 | Bars and de-coiled rods Class B or C<br>With $f_{yk}$ and $k$ according to EN 1992-1-1:2004+AC:2010<br>$f_{tk} = f_{tk} = k \times f_{yk}$<br>Rib height of the bar ( $h$ ) in the range $0,05d \leq h \leq 0,07d$ |

**Table A3: Injection mortars**


| Product   | Composition   |
|---|---|
| BOSSONG BCR V PLUS<br>BOSSONG BCR V PLUS-W<br>BOSSONG BCR V PLUS-T<br>(two component injection mortars) | Additive: quartz<br>Bonding agent: vinyl ester resin styrene free<br>Hardener: dibenzoyl peroxide |

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**


**Product description**  
Materials (2)

**Annex A3**  
of European  
Technical Assessment  
ETA-09/0140


**coaxial cartridge - sizes from 75 ml to 420 ml**

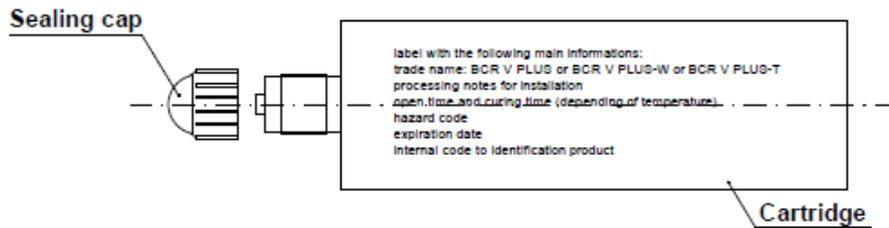


**side by side cartridge - sizes from 345 ml to 825 ml**

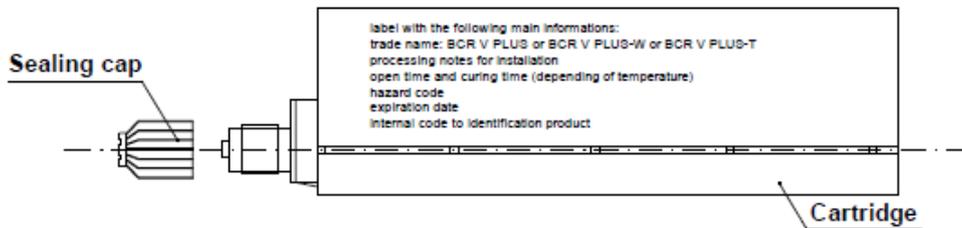


**CIC foil cartridge - sizes from 165 ml to 300 ml**

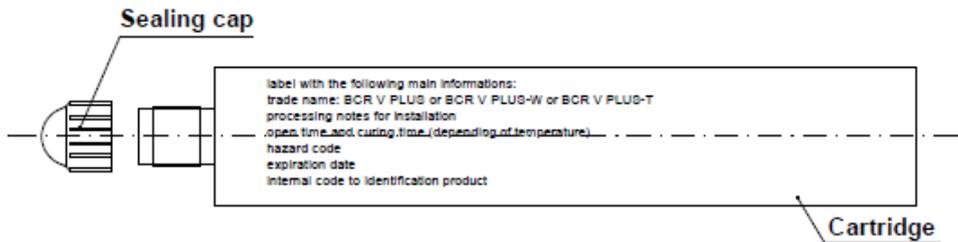

**coaxial peeler cartridge - size of 280 ml**

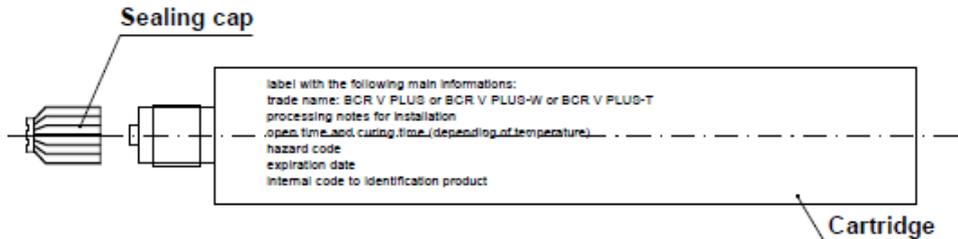

**MIXER - the mixer is suitable for each type of cartridge**

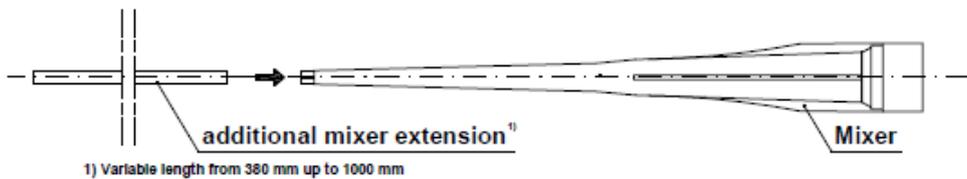

**BOSSONG BCR V PLUS,  
 BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Product description**  
 Cartridge types and sizes

**Annex A4**  
 of European  
 Technical Assessment  
 ETA-09/0140

### Specifications of intended use

**Use:**

The anchors are intended to be used for anchorages for which requirements for mechanical resistance and stability and safety in use in the sense of the Basic Requirement 1 (EU) 305/2011 shall be fulfilled and failure of anchorages made with these products would compromise the stability of the works, cause risk to human life and/or lead to considerable economic consequences.

**Anchors subject to:**

Static and quasi-static loads: sizes from M8 to M30 and from Ø8 to Ø32.

Seismic performance category C1: sizes from M12 to M20, rods with  $f_{uk} \leq 800 \text{ N/mm}^2$  and fracture elongation  $A_5 \geq 19\%$ .

Seismic performance category C2: sizes M12 and M16, rods with  $f_{uk} \leq 800 \text{ N/mm}^2$  and fracture elongation  $A_5 \geq 19\%$ .

**Base material:**

- Reinforced or unreinforced normal weight concrete of strength class C20/25 at minimum to C50/60 at maximum according to EN 206-1:2013+A1:2016.
- Non-cracked concrete: sizes from M8 to M30 and from Ø8 to Ø32.
- Cracked concrete: sizes from M10 to M20.

**Temperature range:**

The anchors may be used in the following temperature range:

- -40°C to +40°C (max. short term temperature +40°C and max. long term temperature +24°C).
- -40°C to +80°C (max. short term temperature +80°C and max. long term temperature +50°C).
- -40°C to +120°C (max. short term temperature +120°C and max. long term temperature +72°C).

**Use conditions (environmental conditions):**

- X1: Structures subject to dry internal conditions: Elements made of galvanized steel (zinc plated or hot dip galvanized) and stainless steel A2, A4 or high corrosion resistance steel (HCR).
- X2: Structures subject to external atmospheric exposure (including industrial and marine environment) and to permanently damp internal condition, if no particular aggressive conditions exist: Elements made of stainless steel A4 or high corrosion resistance steel (HCR).
- X3: Structures subject to external atmospheric exposure (including industrial and marine environment) and to permanently damp internal condition, if other particular aggressive conditions exist. Such particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used): Elements made of high corrosion resistant steel (HCR).


**Installation:**

- Dry or wet concrete (use category I1): sizes from M8 to M30 and from Ø8 to Ø32.
- Flooded holes with the exception of seawater (use category I2): sizes from M8 to M30 and from Ø8 to Ø32.
- Installation direction D3 (downward and horizontal and upwards installation): sizes from M8 to M30 and from Ø8 to Ø32.
- The anchors are suitable for hammer drilled holes (HD), for hollow drill bit (HDB) and for compressed air drill (CA): sizes from M8 to M30 and from Ø8 to Ø32.

**Design methods:**

- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e. g. position of the anchor relative to reinforcement or to supports, etc.).
- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Anchorages under static or quasi-static loads are designed in accordance to EN 1992-4:2018 and Technical Report TR 055.
- Anchorages under seismic actions are designed in accordance to EN 1992-4:2018 and Technical Report TR 045.


|   |   |
|---|---|
| <p><b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b></p> | <p><b>Annex B1</b><br/>of European<br/>Technical Assessment<br/>ETA-09/0140</p> |
| <p><b>Intended use<br/>Specifications</b></p>                                       |   |

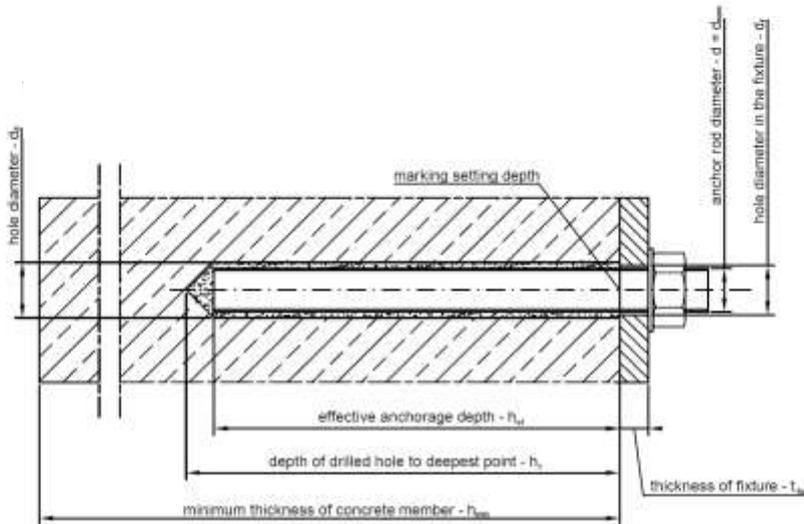

**Table B1: Installation data for threaded rods**

| Size                                   |                    | M8                              | M10 | M12 | M16 | M20             | M24 | M27 | M30 |
|--|--------------------|---------------------------------|-----|-----|-----|-----------------|-----|-----|-----|
| Nominal drilling diameter              | $d_0$ [mm]         | 10                              | 12  | 14  | 18  | 24              | 28  | 30  | 35  |
| Maximum diameter hole in the fixture   | $d_{fix}$ [mm]     | 9                               | 12  | 14  | 18  | 22              | 26  | 30  | 33  |
| Effective embedment depth              | $h_{ef,min}$ [mm]  | 60                              | 70  | 80  | 100 | 120             | 145 | 145 | 145 |
|  | $h_{ef,max}$ [mm]  | 160                             | 200 | 240 | 320 | 400             | 480 | 540 | 600 |
| Depth of the drilling hole             | $h_1$ [mm]         | $h_{ef} + 5$ mm                 |     |     |     |                 |     |     |     |
| Minimum thickness of the concrete slab | $h_{min}$ [mm]     | $h_{ef} + 30$ mm; $\geq 100$ mm |     |     |     | $h_{ef} + 2d_0$ |     |     |     |
| Maximum setting torque moment          | $T_{fix}$ [N·m]    | 10                              | 20  | 40  | 80  | 130             | 200 | 250 | 280 |
| Thickness to be fixed                  | $t_{fix,min}$ [mm] | $> 0$                           |     |     |     |                 |     |     |     |
|  | $t_{fix,max}$ [mm] | $< 1500$                        |     |     |     |                 |     |     |     |
| Minimum spacing                        | $s_{min}$ [mm]     | 40                              | 50  | 60  | 75  | 100             | 115 | 120 | 140 |
| Minimum edge distance                  | $c_{min}$ [mm]     | 40                              | 50  | 60  | 75  | 100             | 115 | 120 | 140 |

|  |   |
|--|---|
| <b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b> | <b>Annex B2</b><br>of European<br>Technical Assessment<br>ETA-09/0140 |
| <b>Intended use</b><br>Installation data for threaded rods                   |   |

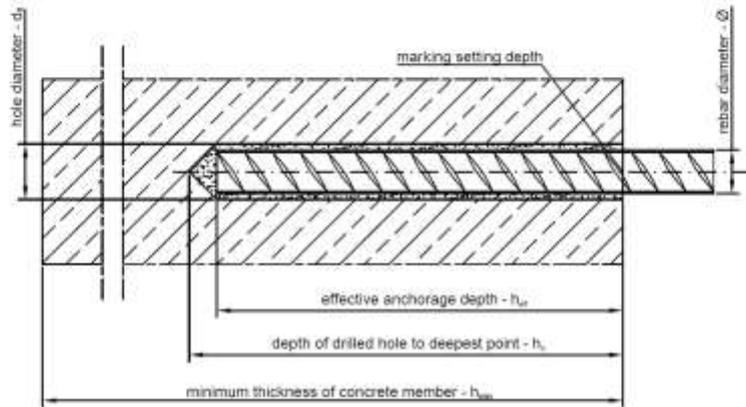

**Table B2: Installation data for rebars**

| Size                                   |                           | Ø8                                   | Ø10                                  | Ø12                                  | Ø14             | Ø16 | Ø20 | Ø25 | Ø28 | Ø32 |
|--|---------------------------|--------------------------------------|--------------------------------------|--------------------------------------|-----------------|-----|-----|-----|-----|-----|
| Nominal drilling diameter              | $d_0$ [mm]                | 10 <sup>1)</sup><br>12 <sup>1)</sup> | 12 <sup>1)</sup><br>14 <sup>1)</sup> | 14 <sup>1)</sup><br>16 <sup>1)</sup> | 18              | 20  | 25  | 30  | 35  | 40  |
|  | Effective embedment depth | $h_{ef,min}$ [mm]                    | 60                                   | 70                                   | 80              | 80  | 100 | 120 | 150 | 180 |
| $h_{ef,max}$ [mm]                      |                           | 160                                  | 200                                  | 240                                  | 280             | 320 | 400 | 500 | 560 | 640 |
| Depth of the drilling hole             | $h_1$ [mm]                | $h_{ef} + 5$ mm                      |                                      |                                      |                 |     |     |     |     |     |
| Minimum thickness of the concrete slab | $h_{min}$ [mm]            | $h_{ef} + 30$ mm;<br>$\geq 100$ mm   |                                      |                                      | $h_{ef} + 2d_0$ |     |     |     |     |     |
| Minimum spacing                        | $s_{min}$ [mm]            | 50                                   | 60                                   | 65                                   | 75              | 80  | 100 | 120 | 140 | 160 |
| Minimum edge distance                  | $c_{min}$ [mm]            | 50                                   | 60                                   | 65                                   | 75              | 80  | 100 | 120 | 140 | 160 |

<sup>1)</sup> Each of two given values can be used

|  |   |
|--|---|
| <b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b> | <b>Annex B3</b><br>of European<br>Technical Assessment<br>ETA-09/0140 |
| <b>Intended use</b><br>Installation data for rebars                          |   |

**Table B3: Maximum processing time and minimum curing time**

| <b>BOSSONG BCR V PLUS (standard version)</b>            |                               |  |
|---|-------------------------------|--|
| <b>Concrete temperature [C°]</b>                        | <b>Processing time [min.]</b> | <b>Minimum curing time<sup>1)</sup> [min.]</b> |
| -10   | 105                           | 1440   |
| -5  | 65                            | 840  |
| 0   | 45                            | 420  |
| +5  | 25                            | 90   |
| +10   | 16                            | 60   |
| +15   | 11,5                          | 45   |
| +20   | 7,5                           | 40   |
| +25   | 5                             | 35   |
| +30   | 3                             | 30   |
| +35   | 2                             | 25   |
| +40   | 1                             | 20   |
| <b>BOSSONG BCR V PLUS-W (version for winter season)</b> |                               |  |
| <b>Concrete temperature [C°]</b>                        | <b>Processing time [min.]</b> | <b>Minimum curing time<sup>1)</sup> [min.]</b> |
| -20   | 120                           | 2880   |
| -15   | 90                            | 1500   |
| -10   | 60                            | 900  |
| -5  | 40                            | 315  |
| 0   | 25                            | 100  |
| +5  | 15                            | 70   |
| +10   | 10                            | 50   |
| +15   | 7                             | 35   |
| +20   | 5                             | 30   |
| <b>BOSSONG BCR V PLUS-T (version for summer season)</b> |                               |  |
| <b>Concrete temperature [C°]</b>                        | <b>Processing time [min.]</b> | <b>Minimum curing time<sup>1)</sup> [min.]</b> |
| +20   | 14                            | 60   |
| +25   | 11                            | 50   |
| +30   | 8                             | 40   |
| +35   | 6                             | 30   |
| +40   | 4                             | 20   |


<sup>1)</sup> The minimum time from the end of the mixing to the time when the anchor may be torque or loaded (whichever is longer). Cartridge temperature from +5°C to +30°C. Minimum cartridge temperature of +15°C for application where the concrete temperature is below 0°C.  
For wet condition and flooded holes the curing time must be double.

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Intended use**  
Maximum processing time and minimum curing time

**Annex B4**  
of European  
Technical Assessment  
ETA-09/0140

**Manual Blower pump: nominal dimensions**

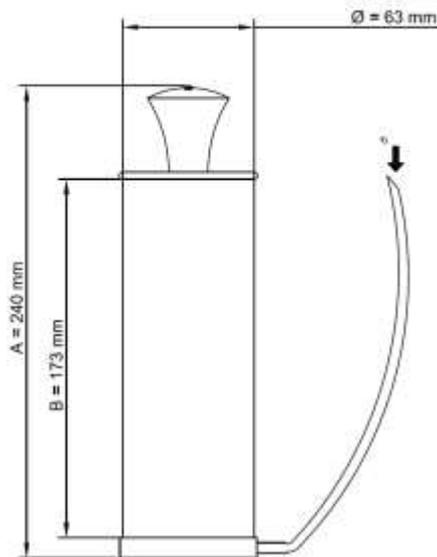

It is possible to use the mixer extensor with the manual blower pump.

However it is possible to blow the hole using the mechanical air system (compressed air) also with the mixer extension



Suitable min pressure 6 bar at 6 m<sup>3</sup>/h  
 Oil-free compressed air  
 Recommended air gun with an orifice opening of minimum 3.5 mm in diameter

1) Position to insert the mixer extension

Mixer extension (from 380 mm to 1000 mm) with nominal diameter 8 or 10 mm

|  |   |
|--|---|
| <p><b>BOSSONG BCR V PLUS,<br/>                 BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b></p> | <p><b>Annex B5</b></p>  |
| <p><b>Intended use</b><br/>                 Cleaning tools (1)</p>                                   | <p>of European<br/>                 Technical Assessment<br/>                 ETA-09/0140</p> |

**Table B4: Standard brush diameter for threaded rods**

| Threaded rod diameter |                         | M8 | M10 | M12 | M16 | M20 | M24 | M27 | M30 |
|-----------------------|-------------------------|----|-----|-----|-----|-----|-----|-----|-----|
| <b>d<sub>0</sub></b>  | Nominal drill hole [mm] | 10 | 12  | 14  | 18  | 24  | 28  | 30  | 35  |
| <b>d<sub>b</sub></b>  | Brush diameter [mm]     | 12 | 14  | 16  | 20  | 26  | 30  | 35  | 37  |

**Table B5: Standard brush diameter for rebar**

| Rebar diameter       |                         | Ø8               | Ø10              |                  | Ø12              |                  | Ø14              |    |
|----------------------|-------------------------|------------------|------------------|------------------|------------------|------------------|------------------|----|
| <b>d<sub>0</sub></b> | Nominal drill hole [mm] | 10 <sup>1)</sup> | 12 <sup>1)</sup> | 12 <sup>1)</sup> | 14 <sup>1)</sup> | 14 <sup>1)</sup> | 16 <sup>1)</sup> | 18 |
| <b>d<sub>b</sub></b> | Brush diameter [mm]     | 12               | 14               | 14               | 16               | 16               | 18               | 20 |

<sup>1)</sup> Each of two given values can be used


**Table B6: Special brush diameter (mechanical brush) for threaded rods**

| Threaded rod diameter |                         | M16 | M20 | M24 | M27 | M30 |
|-----------------------|-------------------------|-----|-----|-----|-----|-----|
| <b>d<sub>0</sub></b>  | Nominal drill hole [mm] | 18  | 24  | 28  | 30  | 35  |
| <b>d<sub>b</sub></b>  | Brush diameter [mm]     | 20  | 26  | 30  | 32  | 37  |

**Table B7: Special brush diameter (mechanical brush) for rebar**

| Threaded rod diameter |                         | Ø8               | Ø10              | Ø12              | Ø14              | Ø16              | Ø20              | Ø25 | Ø28 | Ø32 |    |    |    |
|-----------------------|-------------------------|------------------|------------------|------------------|------------------|------------------|------------------|-----|-----|-----|----|----|----|
| <b>d<sub>0</sub></b>  | Nominal drill hole [mm] | 10 <sup>1)</sup> | 12 <sup>1)</sup> | 12 <sup>1)</sup> | 14 <sup>1)</sup> | 14 <sup>1)</sup> | 16 <sup>1)</sup> | 18  | 20  | 25  | 30 | 35 | 40 |
| <b>d<sub>b</sub></b>  | Brush diameter [mm]     | 12               | 14               | 14               | 16               | 16               | 18               | 20  | 22  | 27  | 32 | 37 | 42 |

<sup>1)</sup> Each of two given values can be used

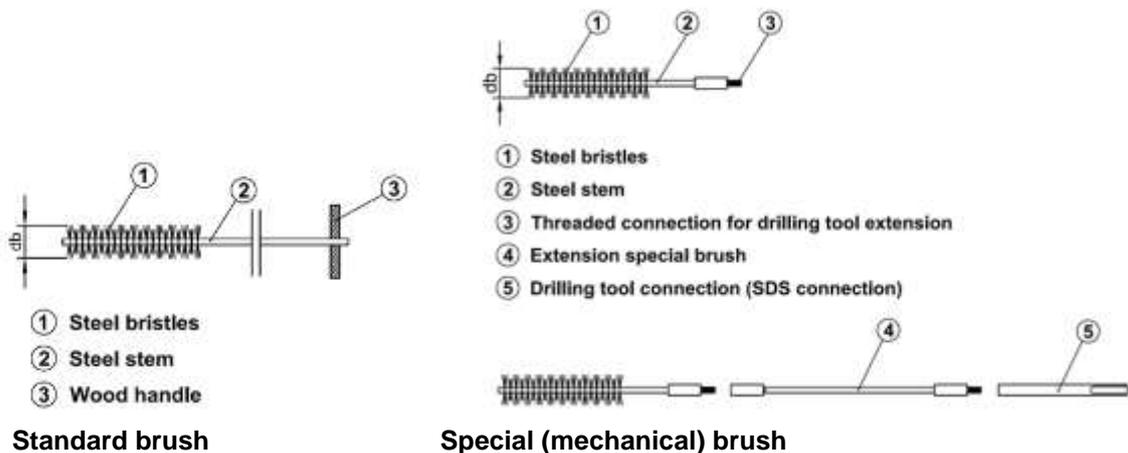

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

---

**Intended use**  
Cleaning tools (2)


**Annex B6**  
of European  
Technical Assessment  
ETA-09/0140

### Hollow Drill Bit (HDB)

This drilling method is a hammer drilling method.

This drilling system removes the dust and cleans the bore hole during the drilling operation when used in accordance with the user's manual.

This drilling system include a vacuum cleaner. A suitable dust extraction system must be used. e.g. Bosch GAS 35 M AFC or a comparable dust extraction system with equivalent performance data.

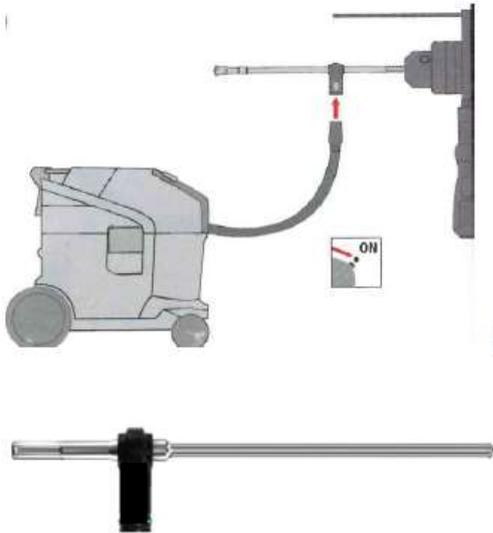

Switch-on the vacuum cleaner before to drill

**Table B8: HDB perforation diameter for threaded rods**

| Threaded rod diameter |                         | M8 | M10 | M12 | M16 | M20 | M24 | M27 | M30 |
|-----------------------|-------------------------|----|-----|-----|-----|-----|-----|-----|-----|
| <b>d<sub>0</sub></b>  | Nominal drill hole [mm] | 10 | 12  | 14  | 18  | 24  | 28  | 30  | 35  |


**Table B9: HDB perforation diameter for rebar**

| Rebar diameter       |                         | Ø8                                   | Ø10                                  | Ø12                                  | Ø14 | Ø16 | Ø20 | Ø25 | Ø28 |
|----------------------|-------------------------|--------------------------------------|--------------------------------------|--------------------------------------|-----|-----|-----|-----|-----|
| <b>d<sub>0</sub></b> | Nominal drill hole [mm] | 10 <sup>1)</sup><br>12 <sup>1)</sup> | 12 <sup>1)</sup><br>14 <sup>1)</sup> | 14 <sup>1)</sup><br>16 <sup>1)</sup> | 18  | 20  | 25  | 30  | 35  |



<sup>1)</sup> Each of two given values can be used

|  |   |
|--|---|
| <b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b> | <b>Annex B7</b><br>of European<br>Technical Assessment<br>ETA-09/0140 |
| <b>Intended use</b><br>Hollow drill bit (HDB) specification                  |   |


**Use the mixer extension (assembled on the standard mixer) for the injection up to 300 mm if necessary.**

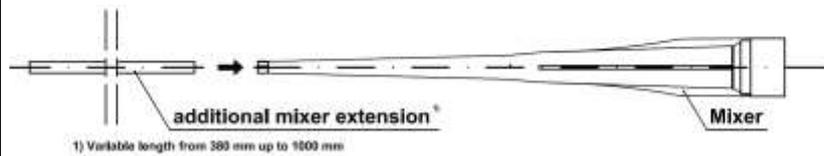

**Use this system for special conditions.**

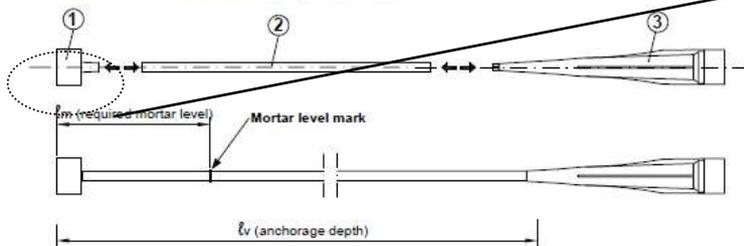

Insert the special mixer extension in the inner diameter of the injection plug up to reach the top of the plug




- ① Injection plug (nominal diameter according to the nominal diameter of drilled hole)
- ② Special mixer extension (variable length with external diameter 10 mm)  
Mark the required mortar level  $\ell_m$  and embedment depth  $\ell_v$  with tape or marker on the injection extension. Quick estimation:  $\ell_m = 1/3 \cdot \ell_v$   
Continue injection until the mortar level mark  $\ell_m$  becomes visible.
- ③ Mixer (suitable for all size of cartridge)

These tools allow the application in special conditions:  
- installation with anchorage depth greater than 300 mm;  
- overhead installation.

For these applications it is recommended the use of pneumatic or battery dispenser.

**System assembled**

- ① Injection plug
- ② Special mixer extension
- ③ Mixer
- ④ Cartridge
- ⑤ Sample of dispenser

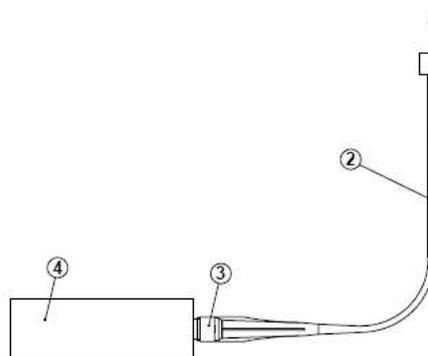

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**






**Annex B8**  
of European  
Technical Assessment  
ETA-09/0140



**Intended use**  
Tools for installation (1)

**Table B10: Mortar injection pumps**

| Pumps (injection dispensers)  | Cartridges                                     | Types                                       |
|---|--|---|
|  <p><i>Manual</i></p>      | 420 ml<br>400 ml<br>380 ml                     | Manual<br>(up to 300 mm anchorage depth)    |
|  <p><i>Manual</i></p>      | 345 ml<br>300 ml<br>280 ml<br>165 ml           | Manual<br>(up to 300 mm anchorage depth)    |
|  <p><i>Manual</i></p>      | 300 ml<br>280 ml<br>165 ml                     | Manual<br>(up to 300 mm anchorage depth)    |
|  <p><i>Pneumatic</i></p>  | 825 ml   | Pneumatic<br>(up to 640 mm anchorage depth) |
|  <p><i>Pneumatic</i></p> | 420 ml<br>400 ml<br>380 ml                     | Pneumatic<br>(up to 640 mm anchorage depth) |
|  <p><i>Battery</i></p>   | 420 ml<br>400 ml<br>380 ml<br>345 ml<br>300 ml | Battery<br>(up to 640 mm anchorage depth)   |




|   |   |
|---|---|
| <p><b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b></p> | <p><b>Annex B9</b><br/>of European<br/>Technical Assessment<br/>ETA-09/0140</p> |
| <p><b>Intended use</b><br/>Tools for installation (2)</p>                           |   |
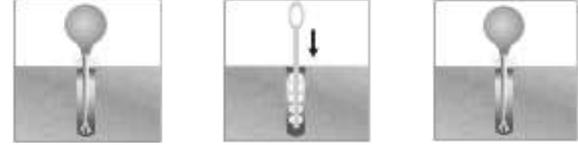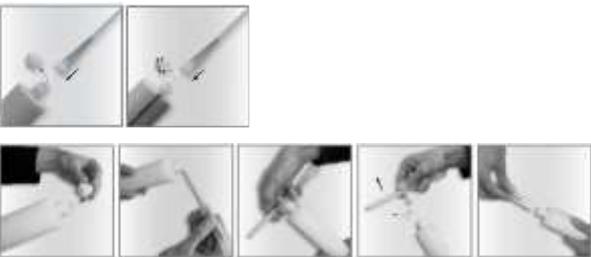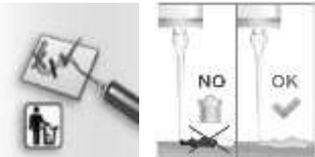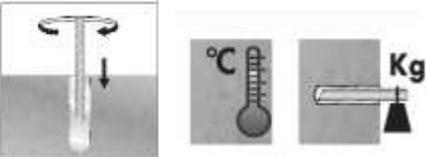
|   |   |   |
|---|---|---|
| <p>1</p>  |    | <p>Drill the hole with the correct diameter and depth using a rotary percussive machine. Check the perpendicularity of the hole during the drilling operation. <b>In case of use of hollow drill bit (Annex B7) proceed directly to the clause 3.</b></p>   |
| <p>2</p>  |  <p>4x blower manual pump<br/>4x standard brush<br/>4x blower manual pump<br/>if necessary use a mixer extension for the blower operation (see Annex B5)</p> | <p>Clean the hole from drilling dust: the hole shall be cleaned by at least 4 blowing operations, by at least 4 brushing operations followed again by at least 4 blowing operations; before brushing clean the brush and check (see Annex B6, standard brush) if the brush diameter is sufficient. For the blower tools see Annex B5.</p>   |
| <p>3</p>  |    | <p>For coaxial, peeler and side by side cartridges unscrew the front cup, screw on the mixer and insert the cartridge into the gun. For CIC sizes, unscrew the front cup, pull-out the steel closing clip according to the following operation:</p> <ol style="list-style-type: none"> <li>1) Insert the mixer in the eye of the plastic extractor;</li> <li>2) Pull the extractor to unhook the steel closing clip of the foil. In the version without the extractor cut the foil pack.</li> </ol> <p>After that screw on the mixer and insert the cartridge in the gun.</p> |
| <p>4</p>  |    | <p>Before starting to use the cartridge, eject a first part of the product, being sure that the two components are completely mixed. The complete mixing is reached only after that the product, obtained by mixing the two components, comes out from the mixer with a uniform colour.</p>   |
| <p>5</p>  |  <p>if necessary, use a mixer extension for the injection (see Annex B8)</p>   | <p>Fill the drilled hole uniformly starting from the drilled hole bottom, in order to avoid entrapment of the air; remove the mixer slowly bit by bit during pressing-out; filling the drill hole with a quantity of the injection mortar corresponding to 2/3 of the drill hole depth.</p>   |
| <p>6</p>  |  <p>ATTENTION: Steel elements dry and free oil and other contaminants</p>  | <p>Insert immediately the steel element (threaded rod or rebar), marked according to the proper anchorage depth, slowly and with a slight twisting motion, removing excess of injection mortar around the steel element. Observe the processing time according Annex B4. Wait the curing time according Annex B4.</p>   |
| <p><b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b></p> |   | <p><b>Annex B10</b><br/>of European<br/>Technical Assessment<br/>ETA-09/0140</p>  |
| <p><b>Intended use</b><br/>Installation instruction up to 300 mm depth</p>          |   |   |
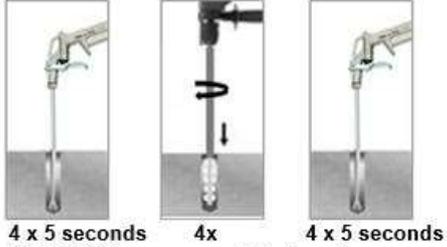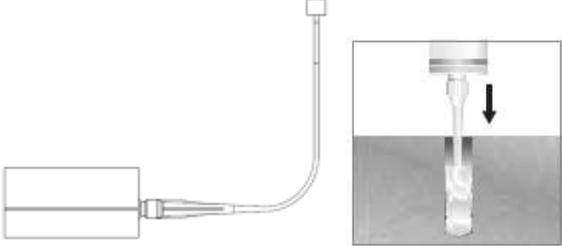
|   |  |   |
|---|--|---|
| 1   | <p>See clause 1 Annex B10. In case of use of hollow drill bit (HDB) proceed directly to the clause 3.</p>  |   |
| 2   |  <p>4 x 5 seconds    4x    4 x 5 seconds<br/>ATTENTION: compressed air free oil</p> | <p>Clean the hole from drilling dust:<br/>the hole shall be cleaned by at least 4 blowing operations (5 seconds for single operation) with compressed air, by at least 4 brushing operations with special brush followed again by at least 4 blowing operations (5 seconds for single operation) with compressed air. Before brushing clean the brush and check if the brush diameter is sufficient.</p>  |
| 3   | <p>See clause 3 Annex B10</p>  |   |
| 4   | <p>See clause 4 Annex B10</p>  |   |
| 5   |   | <p>Before starting the injection, assemble the system according to Annex B8. After that, fill the drilled hole uniformly from the drilled hole bottom, in order to avoid entrapment of the air; remove the special mixer extension with injection plug slowly bit by bit during pressing-out; filling the drill hole with a quantity of the injection mortar corresponding to 2/3 of the drill hole depth.<br/>Procedure for overhead installation are detailed in Annex B12.</p> |
| 6   | <p>See clause 6 Annex B10</p>  |   |
| <p><b>BOSSONG BCR V PLUS,<br/>BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T</b></p> |  | <p><b>Annex B11</b></p>   |
| <p><b>Intended use</b><br/>Installation instruction up to 640 mm depth</p>          |  | <p>of European<br/>Technical Assessment<br/>ETA-09/0140</p>   |

## Overhead installation procedure

In addition to standard procedure, for overhead installation, following the below procedure
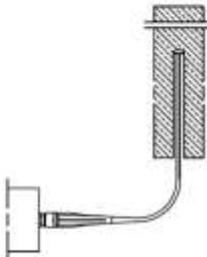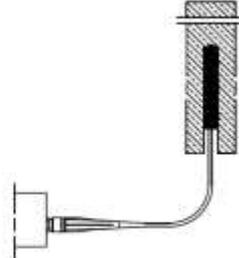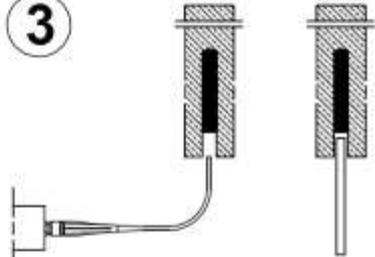
|  |   |
|--|---|
| <p>①</p>    | <p><b>1 - Start injection</b></p> <p>Inject from the bottom of the hole. Use battery or pneumatic dispenser if the anchorage depth is grater than 200 mm.</p>   |
| <p>②</p>   | <p><b>2 - Injection phase</b></p> <p>Inject the product about 2/3 of the hole depth. Remove the mixer extension slowly bit by bit during pressing-out.</p>  |
| <p>③</p>  | <p><b>3 - End injection</b></p> <p>Remove the mixer extension. Insert immediately the steel element (turn the steel element during the insertion).</p>  |
| <p>④</p>  | <p><b>4 - End installation</b></p> <p>To avoid the slipping of the steel element during the open time of the product (due to the steel element own weigth) use a temporary interlocking element (for ex. wedge of wood)</p> |

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Intended use**  
Overhead installation instruction

**Annex B12**  
of European  
Technical Assessment  
ETA-09/0140

**Table C1: Characteristic values for steel tension resistance and steel shear resistance – threaded rods.**

| Size  |                          | M8 | M10 | M12 | M16 | M20  | M24  | M27  | M30  |  |
|---|--------------------------|----|-----|-----|-----|------|------|------|------|--|
| <b>Steel failure – characteristic tension resistance</b>                  |                          |    |     |     |     |      |      |      |      |  |
| Steel class 4.8   | $N_{Rk,s}$ [kN]          | 15 | 23  | 34  | 63  | 98   | 141  | 183  | 224  |  |
| Steel class 5.8   | $N_{Rk,s}$ [kN]          | 18 | 29  | 42  | 78  | 122  | 176  | 229  | 280  |  |
| Steel class 8.8   | $N_{Rk,s}$ [kN]          | 29 | 46  | 67  | 126 | 196  | 282  | 367  | 449  |  |
| Steel class 10.9  | $N_{Rk,s}$ [kN]          | 37 | 58  | 84  | 157 | 245  | 353  | 459  | 561  |  |
| Stainless steel A2, A4, HCR class 50                                      | $N_{Rk,s}$ [kN]          | 18 | 29  | 42  | 78  | 122  | 176  | 229  | 280  |  |
| Stainless steel A2, A4, HCR class 70                                      | $N_{Rk,s}$ [kN]          | 26 | 41  | 59  | 110 | 171  | 247  | 321  | 392  |  |
| Stainless steel A4, HCR class 80  | $N_{Rk,s}$ [kN]          | 29 | 46  | 67  | 126 | 196  | 282  | 367  | 449  |  |
| <b>Steel failure – characteristic tension resistance – partial factor</b> |                          |    |     |     |     |      |      |      |      |  |
| Steel class 4.8   | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,50 |      |      |      |  |
| Steel class 5.8   | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,50 |      |      |      |  |
| Steel class 8.8   | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,50 |      |      |      |  |
| Steel class 10.9  | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,40 |      |      |      |  |
| Stainless steel A2, A4, HCR class 50                                      | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 2,86 |      |      |      |  |
| Stainless steel A2, A4, HCR class 70                                      | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,87 |      |      |      |  |
| Stainless steel A4, HCR class 80  | $\gamma_{Ms,N}^{1)}$ [-] |    |     |     |     | 1,60 |      |      |      |  |
| <b>Steel failure – characteristic shear resistance without lever arm</b>  |                          |    |     |     |     |      |      |      |      |  |
| Steel class 4.8   | $V_{Rk,s}^0$ [kN]        | 7  | 12  | 17  | 31  | 49   | 71   | 92   | 112  |  |
| Steel class 5.8   | $V_{Rk,s}^0$ [kN]        | 9  | 14  | 21  | 39  | 61   | 88   | 115  | 140  |  |
| Steel class 8.8   | $V_{Rk,s}^0$ [kN]        | 15 | 23  | 34  | 63  | 98   | 141  | 184  | 224  |  |
| Steel class 10.9  | $V_{Rk,s}^0$ [kN]        | 18 | 29  | 42  | 78  | 122  | 176  | 230  | 280  |  |
| Stainless steel A2, A4, HCR class 50                                      | $V_{Rk,s}^0$ [kN]        | 9  | 14  | 21  | 39  | 61   | 88   | 115  | 140  |  |
| Stainless steel A2, A4, HCR class 70                                      | $V_{Rk,s}^0$ [kN]        | 13 | 20  | 29  | 55  | 86   | 124  | 160  | 196  |  |
| Stainless steel A4, HCR class 80  | $V_{Rk,s}^0$ [kN]        | 15 | 23  | 34  | 63  | 98   | 141  | 184  | 224  |  |
| <b>Steel failure – characteristic shear resistance with lever arm</b>     |                          |    |     |     |     |      |      |      |      |  |
| Steel class 4.8   | $M_{Rk,s}^0$ [Nm]        | 15 | 30  | 52  | 133 | 260  | 449  | 666  | 900  |  |
| Steel class 5.8   | $M_{Rk,s}^0$ [Nm]        | 19 | 37  | 65  | 166 | 324  | 561  | 832  | 1125 |  |
| Steel class 8.8   | $M_{Rk,s}^0$ [Nm]        | 30 | 60  | 105 | 266 | 519  | 898  | 1331 | 1799 |  |
| Steel class 10.9  | $M_{Rk,s}^0$ [Nm]        | 37 | 75  | 131 | 333 | 649  | 1123 | 1664 | 2249 |  |
| Stainless steel A2, A4, HCR class 50                                      | $M_{Rk,s}^0$ [Nm]        | 19 | 37  | 66  | 166 | 324  | 561  | 832  | 1124 |  |
| Stainless steel A2, A4, HCR class 70                                      | $M_{Rk,s}^0$ [Nm]        | 26 | 52  | 92  | 233 | 454  | 786  | 1165 | 1574 |  |
| Stainless steel A4, HCR class 80  | $M_{Rk,s}^0$ [Nm]        | 30 | 60  | 105 | 266 | 519  | 898  | 1331 | 1799 |  |
| <b>Steel failure – characteristic shear resistance – partial factor</b>   |                          |    |     |     |     |      |      |      |      |  |
| Steel class 4.8   | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,25 |      |      |      |  |
| Steel class 5.8   | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,25 |      |      |      |  |
| Steel class 8.8   | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,25 |      |      |      |  |
| Steel class 10.9  | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,50 |      |      |      |  |
| Stainless steel A2, A4, HCR class 50                                      | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 2,38 |      |      |      |  |
| Stainless steel A2, A4, HCR class 70                                      | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,56 |      |      |      |  |
| Stainless steel A4, HCR class 80  | $\gamma_{Ms,V}^{1)}$ [-] |    |     |     |     | 1,33 |      |      |      |  |

Fracture elongation threaded rod for seismic category C1 and C2 must be  $A_s \geq 19\%$ .

Steel classes 10.9 are not covered for seismic application.

<sup>1)</sup> In the absence of national regulation

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**  
Characteristic values for steel tension resistance and steel shear resistance  
- threaded rods

**Annex C1**  
of European  
Technical Assessment  
ETA-09/0140

**Table C2: Characteristic values tension resistance load in non-cracked concrete for threaded rod under static and quasi-static loads**

| Size  |                      |                      | M8                                 | M10                | M12                | M16  | M20 | M24 | M27 | M30 |
|---|----------------------|----------------------|------------------------------------|--------------------|--------------------|------|-----|-----|-----|-----|
| <b>Steel failure</b>  |                      |                      |                                    |                    |                    |      |     |     |     |     |
| Characteristic resistance   | $N_{Rk,s}$           | [kN]                 | See Annex C1 – Table C1            |                    |                    |      |     |     |     |     |
| Partial factor  | $\gamma_{Ms,N}^{1)}$ | [-]                  | See Annex C1 – Table C1            |                    |                    |      |     |     |     |     |
| <b>Combined pull-out and concrete cone failure in non-cracked concrete C20/25</b>     |                      |                      |                                    |                    |                    |      |     |     |     |     |
| Characteristic bond resistance temperature range -40°C / +40°C                        | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 16,0                               | 12,0               | 12,0               | 12,0 | 9,5 | 9,5 | 8,0 | 8,0 |
| Characteristic bond resistance temperature range -40°C / +80°C                        | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 11,0                               | 8,5                | 8,5                | 8,5  | 7,0 | 7,0 | 6,0 | 6,0 |
| Characteristic bond resistance temperature range -40°C / +120°C                       | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 6,0                                | 4,5                | 4,5                | 4,5  | 4,0 | 4,0 | 3,0 | 3,0 |
| Increasing factor for C30/37  | $\psi_c$             | [-]                  | 1,12                               |                    |                    |      |     |     |     |     |
| Increasing factor for C40/50  |                      |                      | 1,23                               |                    |                    |      |     |     |     |     |
| Increasing factor for C50/60  |                      |                      | 1,30                               |                    |                    |      |     |     |     |     |
| <b>Concrete cone failure</b>  |                      |                      |                                    |                    |                    |      |     |     |     |     |
| Factor for non-cracked concrete   | $k_{ucr,N}$          | [-]                  | 11,0                               |                    |                    |      |     |     |     |     |
| Edge distance   | $C_{cr,N}$           | [mm]                 | $1,5 h_{ef}$                       |                    |                    |      |     |     |     |     |
| Spacing   | $S_{cr,N}$           | [mm]                 | $3,0 h_{ef}$                       |                    |                    |      |     |     |     |     |
| <b>Splitting failure</b>  |                      |                      |                                    |                    |                    |      |     |     |     |     |
| Edge distance   | $C_{cr,Nsp}$         | [mm]                 | If $h = h_{min}$                   |                    |                    |      |     |     |     |     |
|   |                      |                      | $2,5 \cdot h_{ef}$                 | $2,0 \cdot h_{ef}$ | $1,5 \cdot h_{ef}$ |      |     |     |     |     |
|   |                      |                      | If $h_{min} < h < 2 \cdot h_{min}$ |                    |                    |      |     |     |     |     |
|   |                      |                      | <p>interpolate values</p>          |                    |                    |      |     |     |     |     |
|   |                      |                      | if $h \geq 2 \cdot h_{min}$        |                    |                    |      |     |     |     |     |
| Spacing   | $S_{cr,Nsp}$         | [mm]                 | $2 \cdot C_{cr,Nsp}$               |                    |                    |      |     |     |     |     |
| <b>Installation factor for combined pull-out, concrete cone and splitting failure</b> |                      |                      |                                    |                    |                    |      |     |     |     |     |
| Installation factors for category I1 <sup>1)</sup>                                    | $\gamma_{inst}$      | [-]                  | 1,0                                |                    |                    |      |     |     |     |     |
| Installation factors for category I2 <sup>1)</sup>                                    |                      |                      | 1,2                                |                    |                    |      |     |     |     |     |

<sup>1)</sup> In the absence of national regulation

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**

Characteristic values tension resistance load in non-cracked concrete for threaded rod under static and quasi-static loads

**Annex C2**  
of European  
Technical Assessment  
ETA-09/0140

**Table C3: Characteristic values tension resistance load in cracked concrete for threaded rod under static and quasi-static loads**

| Size  |                               |                      | M10  | M12            | M16            | M20 |
|---|-------------------------------|----------------------|--|----------------|----------------|-----|
| <b>Steel failure</b>  |                               |                      |  |                |                |     |
| Characteristic resistance   | $N_{Rk,s}$                    | [kN]                 | See Annex C1 – Table C1                    |                |                |     |
| Partial factor  | $\gamma_{Ms,N}$ <sup>1)</sup> | [-]                  | See Annex C1 – Table C1                    |                |                |     |
| <b>Combined pull-out and concrete cone failure in cracked concrete C20/25</b>         |                               |                      |  |                |                |     |
| Characteristic bond resistance temperature range -40°C / +40°C                        | $\tau_{Rk,cr}$                | [N/mm <sup>2</sup> ] | 9,0  | 9,0            | 9,0            | 6,5 |
| Characteristic bond resistance temperature range -40°C / +80°C                        | $\tau_{Rk,cr}$                | [N/mm <sup>2</sup> ] | 6,5  | 6,5            | 6,5            | 4,5 |
| Characteristic bond resistance temperature range -40°C / +120°C                       | $\tau_{Rk,cr}$                | [N/mm <sup>2</sup> ] | 3,5  | 3,5            | 3,5            | 2,5 |
| Increasing factor for C30/37  | $\psi_c$                      | [-]                  | 1,12                                       |                |                |     |
| Increasing factor for C40/50  |                               |                      | 1,23                                       |                |                |     |
| Increasing factor for C50/60  |                               |                      | 1,30                                       |                |                |     |
| <b>Concrete cone failure</b>  |                               |                      |  |                |                |     |
| Factor for cracked concrete   | $k_{cr,N}$                    | [-]                  | 7,7  |                |                |     |
| Edge distance   | $C_{cr,N}$                    | [mm]                 | 1,5 $h_{ef}$                               |                |                |     |
| Spacing   | $S_{cr,N}$                    | [mm]                 | 3,0 $h_{ef}$                               |                |                |     |
| <b>Splitting failure</b>  |                               |                      |  |                |                |     |
| Edge distance   | $C_{cr,Nsp}$                  | [mm]                 | If $h = h_{min}$                           |                |                |     |
|   |                               |                      | 2,5 · $h_{ef}$                             | 2,0 · $h_{ef}$ | 1,5 · $h_{ef}$ |     |
|   |                               |                      | If $h_{min} < h < 2 \cdot h_{min}$         |                |                |     |
|   |                               |                      |  |                |                |     |
|   |                               |                      | $C_{cr,Np}$<br>if $h \geq 2 \cdot h_{min}$ |                |                |     |
| Spacing   | $S_{cr,Nsp}$                  | [mm]                 | $2 \cdot C_{cr,sp}$                        |                |                |     |
| <b>Installation factor for combined pull-out, concrete cone and splitting failure</b> |                               |                      |  |                |                |     |
| Installation factors for category I1 <sup>1)</sup>                                    | $\gamma_{inst}$               | [-]                  | 1,0  |                |                |     |
| Installation factors for category I2 <sup>1)</sup>                                    |                               |                      | 1,2  |                |                |     |

<sup>1)</sup> In the absence of other national regulation

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Annex C3**  
of European  
Technical Assessment  
ETA-09/0140

**Performances**

Characteristic values tension resistance load in cracked concrete for threaded rod under static and quasi-static loads

**Table C4: Characteristic values shear resistance load – non-cracked and cracked concrete for threaded rod under static and quasi-static loads.**

| Size   |                      |      | M8                                   | M10 | M12 | M16 | M20 | M24 | M27   | M30 |  |
|--|----------------------|------|--------------------------------------|-----|-----|-----|-----|-----|---|-----|--|
| <b>Steel failure without lever arm</b>         |                      |      |                                      |     |     |     |     |     |   |     |  |
| Characteristic resistance                      | $V_{Rk,s}^0$         | [kN] | See Annex C1 – Table C1              |     |     |     |     |     |   |     |  |
| Partial factor                                 | $\gamma_{Ms,V}^{1)}$ | [-]  | See Annex C1 – Table C1              |     |     |     |     |     |   |     |  |
| Ductility factor                               | $k_7$                | [-]  | 1,0                                  |     |     |     |     |     |   |     |  |
| <b>Steel failure with lever arm</b>            |                      |      |                                      |     |     |     |     |     |   |     |  |
| Characteristic resistance                      | $M_{Rk,s}^0$         | [kN] | See Annex C1 – Table C1              |     |     |     |     |     |   |     |  |
| Partial factor                                 | $\gamma_{Ms,V}^{1)}$ | [-]  | See Annex C1 – Table C1              |     |     |     |     |     |   |     |  |
| <b>Concrete pry out failure</b>                |                      |      |                                      |     |     |     |     |     |   |     |  |
| Factor   | $k_8$                | [-]  | 2,0                                  |     |     |     |     |     |   |     |  |
| Installation factor                            | $\gamma_{inst}$      | [-]  | 1,0                                  |     |     |     |     |     |   |     |  |
| <b>Concrete edge failure</b>                   |                      |      |                                      |     |     |     |     |     |   |     |  |
| Effective length of anchor under shear loading | $l_f$                | [-]  | $l_f = h_{ef}$ and $\leq 12 d_{nom}$ |     |     |     |     |     | $l_f = h_{ef}$ and $\leq \max(8 d_{nom}, 300 \text{ mm})$ |     |  |
| Installation factor                            | $\gamma_{inst}$      | [-]  | 1,0                                  |     |     |     |     |     |   |     |  |

<sup>1)</sup> In the absence of other national regulation


**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**

Characteristic values shear resistance load – non- cracked and cracked concrete for threaded rod under static and quasi-static loads.

**Annex C4**  
of European  
Technical Assessment  
ETA-09/0140

**Table C5: Characteristic values tension resistance load in non-cracked concrete for rebar under static and quasi-static loads.**

| Size  |                      |                      | Ø8  | Ø10  | Ø12  | Ø14                | Ø16  | Ø20 | Ø25                | Ø28 | Ø32 |
|---|----------------------|----------------------|---|------|------|--------------------|------|-----|--------------------|-----|-----|
| <b>Steel failure</b>  |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Characteristic resistance   | $N_{Rk,s}$           | [kN]                 | $A_s \times f_{uk}^{2)}$  |      |      |                    |      |     |                    |     |     |
| Cross section area  | $A_s$                | [mm <sup>2</sup> ]   | 50  | 79   | 113  | 154                | 201  | 314 | 491                | 616 | 804 |
| Partial factor  | $\gamma_{Ms,N}^{1)}$ | [-]                  | 1,4   |      |      |                    |      |     |                    |     |     |
| <b>Combined pull-out and concrete cone failure in non cracked concrete C20/25</b>     |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Characteristic bond resistance temperature range -40°C / +40°C                        | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 14,0  | 13,0 | 13,0 | 12,0               | 10,0 | 9,5 | 9,5                | 8,5 | 7,5 |
| Characteristic bond resistance temperature range -40°C / +80°C                        | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 10,0  | 9,5  | 9,0  | 9,0                | 7,5  | 7,0 | 7,0                | 6,0 | 5,5 |
| Characteristic bond resistance temperature range -40°C / +120°C                       | $\tau_{Rk,ucr}$      | [N/mm <sup>2</sup> ] | 5,5   | 5,0  | 5,0  | 5,0                | 4,0  | 4,0 | 4,0                | 3,5 | 3,0 |
| Increasing factor for C30/37  | $\psi_c$             | [-]                  | 1,12  |      |      |                    |      |     |                    |     |     |
| Increasing factor for C40/50  |                      |                      | 1,23  |      |      |                    |      |     |                    |     |     |
| Increasing factor for C50/60  |                      |                      | 1,30  |      |      |                    |      |     |                    |     |     |
| <b>Concrete cone failure</b>  |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Factor for non-cracked concrete   | $k_{ucr,N}$          | [-]                  | 11,0  |      |      |                    |      |     |                    |     |     |
| Edge distance   | $C_{cr,N}$           | [mm]                 | $1,5 \cdot h_{ef}$  |      |      |                    |      |     |                    |     |     |
| Spacing   | $S_{cr,N}$           | [mm]                 | $3,0 \cdot h_{ef}$  |      |      |                    |      |     |                    |     |     |
| <b>Splitting failure</b>  |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Edge distance   | $C_{cr,Nsp}$         | [mm]                 | If $h = h_{min}$  |      |      |                    |      |     |                    |     |     |
|   |                      |                      | $2,5 \cdot h_{ef}$  |      |      | $2,0 \cdot h_{ef}$ |      |     | $1,5 \cdot h_{ef}$ |     |     |
|   |                      |                      | If $h_{min} < h < 2 \cdot h_{min}$  |      |      |                    |      |     |                    |     |     |
|   |                      |                      |  <p>interpolate values</p> |      |      |                    |      |     |                    |     |     |
| if $h \geq 2 \cdot h_{min}$   |                      |                      |   |      |      |                    |      |     |                    |     |     |
| $C_{cr,Np}$   |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Spacing   | $S_{cr,Nsp}$         | [mm]                 | $2 \cdot C_{cr,sp}$   |      |      |                    |      |     |                    |     |     |
| <b>Installation factor for combined pull-out, concrete cone and splitting failure</b> |                      |                      |   |      |      |                    |      |     |                    |     |     |
| Installation factors for category I1 <sup>1)</sup>                                    | $\gamma_{inst}$      | [-]                  | 1,0   |      |      |                    |      |     |                    |     |     |
| Installation factors for category I2 <sup>1)</sup>                                    |                      |                      | 1,2   |      |      |                    |      |     |                    |     |     |

<sup>1)</sup> In the absence of other national regulation

<sup>2)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**

Characteristic values tension resistance load in non-cracked concrete for rebar under static and quasi-static loads.

**Annex C5**  
of European  
Technical Assessment  
ETA-09/0140

**Table C6: Characteristic values shear resistance load – non-cracked concrete for rebar under static and quasi-static loads.**

| Size   |                      |                    | Ø8  | Ø10 | Ø12 | Ø14 | Ø16 | Ø20 | Ø25  | Ø28  | Ø32  |  |
|--|----------------------|--------------------|---|-----|-----|-----|-----|-----|--|------|------|--|
| <b>Steel failure without lever arm</b>         |                      |                    |   |     |     |     |     |     |  |      |      |  |
| Characteristic resistance                      | $V_{Rk,s}^0$         | [kN]               | $0,5 \times A_s \times f_{uk}^{2)}$         |     |     |     |     |     |  |      |      |  |
| Partial factor                                 | $\gamma_{Ms,V}^{1)}$ | [-]                | 1,5   |     |     |     |     |     |  |      |      |  |
| Cross section area                             | $A_s$                | [mm <sup>2</sup> ] | 50  | 79  | 113 | 154 | 201 | 314 | 491  | 616  | 804  |  |
| Ductility factor                               | $k_7$                | [-]                | 1,0   |     |     |     |     |     |  |      |      |  |
| <b>Steel failure with lever arm</b>            |                      |                    |   |     |     |     |     |     |  |      |      |  |
| Characteristic resistance                      | $M_{Rk,s}^0$         | [kN]               | $1,2 \times W_{el} \times f_{uk}^{2)}$      |     |     |     |     |     |  |      |      |  |
| Elastic section modulus                        | $W_{el}$             | [mm <sup>3</sup> ] | 50  | 98  | 170 | 269 | 402 | 785 | 1534   | 2155 | 3217 |  |
| Partial factor                                 | $\gamma_{Ms,V}^{1)}$ | [-]                | 1,5   |     |     |     |     |     |  |      |      |  |
| <b>Concrete pry out failure</b>                |                      |                    |   |     |     |     |     |     |  |      |      |  |
| Factor   | $k_8$                | [-]                | 2,0   |     |     |     |     |     |  |      |      |  |
| Installation factor                            | $\gamma_{inst}$      | [-]                | 1,0   |     |     |     |     |     |  |      |      |  |
| <b>Concrete edge failure</b>                   |                      |                    |   |     |     |     |     |     |  |      |      |  |
| Effective length of anchor under shear loading | $l_f$                | [-]                | $l_f = h_{ef} \text{ and } \leq 12 d_{nom}$ |     |     |     |     |     | $l_f = h_{ef} \text{ and } \leq \max(8 d_{nom}; 300 \text{ mm})$ |      |      |  |
| Installation factor                            | $\gamma_{inst}$      | [-]                | 1,0   |     |     |     |     |     |  |      |      |  |

<sup>1)</sup> In the absence of other national regulation

<sup>2)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**  
Characteristic values shear resistance load – non-cracked concrete for rebar under static and quasi-static loads.

**Annex C6**  
of European  
Technical Assessment  
ETA-09/0140

**Table C7. Displacement under tension loads for non-cracked concrete – threaded rods under static and quasi-static loads.**

| Size  |                    |      | M8   | M10  | M12  | M16  | M20  | M24  | M27  | M30  |
|---|--------------------|------|------|------|------|------|------|------|------|------|
| <b>Characteristic displacement in non-cracked concrete C20/25 to C50/60 under tension loads</b> |                    |      |      |      |      |      |      |      |      |      |
| Service load <sup>1)</sup>  | F                  | [kN] | 9,6  | 10,8 | 14,3 | 23,8 | 29,6 | 42,4 | 40,4 | 44,4 |
| Displacement  | $\delta_{N0}$      | [mm] | 0,30 | 0,30 | 0,35 | 0,35 | 0,35 | 0,40 | 0,40 | 0,45 |
|   | $\delta_{N\infty}$ | [mm] | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 |

**Table C8: Displacement under tension loads for non-cracked concrete – threaded rods under static and quasi-static loads.**

| Size  |                    |      | M10  | M12  | M16  | M20  |
|---|--------------------|------|------|------|------|------|
| <b>Characteristic displacement in cracked concrete C20/25 to C50/60 under tension loads</b> |                    |      |      |      |      |      |
| Service load <sup>1)</sup>  | F                  | [kN] | 9,5  | 14,3 | 21,4 | 23,8 |
| Displacement  | $\delta_{N0}$      | [mm] | 0,50 | 0,50 | 0,70 | 0,60 |
|   | $\delta_{N\infty}$ | [mm] | 0,85 | 0,85 | 0,85 | 0,85 |

**Table C9: Displacement under shear loads for non-cracked and cracked concrete – threaded rods under static and quasi-static loads.**

| Size  |                    |      | M8  | M10 | M12 | M16  | M20  | M24  | M27  | M30  |
|---|--------------------|------|-----|-----|-----|------|------|------|------|------|
| <b>Characteristic displacement in cracked and non-cracked concrete C20/25 to C50/60 under shear loads</b> |                    |      |     |     |     |      |      |      |      |      |
| Service load <sup>1)</sup>  | F                  | [kN] | 3,7 | 5,8 | 8,4 | 15,7 | 24,5 | 35,3 | 45,5 | 55,6 |
| Displacement  | $\delta_{V0}$      | [mm] | 2,0 | 2,0 | 2,0 | 2,0  | 2,0  | 2,0  | 2,0  | 2,0  |
|   | $\delta_{V\infty}$ | [mm] | 3,0 | 3,0 | 3,0 | 3,0  | 3,0  | 3,0  | 3,0  | 3,0  |

**Table C10: Displacement under tension loads for non-cracked concrete – rebar under static and quasi-static loads.**

| Size  |                    |      | Ø8   | Ø10  | Ø12  | Ø14  | Ø16  | Ø20  | Ø25  | Ø28  | Ø32  |
|---|--------------------|------|------|------|------|------|------|------|------|------|------|
| <b>Characteristic displacement in non-cracked concrete C20/25 to C50/60 under tension loads</b> |                    |      |      |      |      |      |      |      |      |      |      |
| Service load <sup>1)</sup>  | F                  | [kN] | 10,1 | 13,6 | 17,2 | 20,1 | 23,9 | 41,2 | 53,3 | 64,1 | 67,3 |
| Displacement  | $\delta_{N0}$      | [mm] | 0,33 | 0,33 | 0,40 | 0,41 | 0,42 | 0,45 | 0,45 | 0,47 | 0,48 |
|   | $\delta_{N\infty}$ | [mm] | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 | 0,85 |

**Table C11: Displacement under shear loads for non-cracked concrete – rebar under static and quasi-static loads.**

| Size  |                    |      | Ø8   | Ø10  | Ø12  | Ø14  | Ø16  | Ø20  | Ø25   | Ø28   | Ø32   |
|---|--------------------|------|------|------|------|------|------|------|-------|-------|-------|
| <b>Characteristic displacement in non-cracked concrete C20/25 to C50/60 under shear loads</b> |                    |      |      |      |      |      |      |      |       |       |       |
| Service load <sup>1)</sup>  | F                  | [kN] | 13,2 | 20,6 | 29,6 | 40,3 | 52,7 | 82,3 | 128,6 | 161,3 | 210,6 |
| Displacement  | $\delta_{V0}$      | [mm] | 2,0  | 2,0  | 2,0  | 2,0  | 2,0  | 2,0  | 2,0   | 2,0   | 2,0   |
|   | $\delta_{V\infty}$ | [mm] | 3,0  | 3,0  | 3,0  | 3,0  | 3,0  | 3,0  | 3,0   | 3,0   | 3,0   |

<sup>1)</sup> These values are suitable for each temperature range and categories specified in Annex B1

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**  
Displacement under service loads

**Annex C7**  
of European  
Technical Assessment  
ETA-09/0140

**Table C12: Characteristic values tension resistance load for threaded rod for seismic performance category C1.**

| Size  |                               |                      | M12                     | M16 | M20 |
|---|-------------------------------|----------------------|-------------------------|-----|-----|
| <b>Steel failure</b>  |                               |                      |                         |     |     |
| Characteristic resistance                                       | $N_{Rk,s,eq,C1}$              | [kN]                 | $1,0 \times N_{Rk,s}$   |     |     |
| Partial factor <sup>1)</sup>                                    | $\gamma_{Ms,N}$ <sup>1)</sup> | [-]                  | See Annex C1 – Table C1 |     |     |
| <b>Combined pull-out and concrete cone failure</b>              |                               |                      |                         |     |     |
| Characteristic bond resistance temperature range -40°C / +40°C  | $\tau_{Rk,C1}$                | [N/mm <sup>2</sup> ] | 4,2                     | 3,7 | 3,7 |
| Characteristic bond resistance temperature range -40°C / +80°C  | $\tau_{Rk,C1}$                | [N/mm <sup>2</sup> ] | 3,0                     | 2,7 | 2,7 |
| Characteristic bond resistance temperature range -40°C / +120°C | $\tau_{Rk,C1}$                | [N/mm <sup>2</sup> ] | 1,6                     | 1,4 | 1,4 |
| Increasing factor for C30/37                                    | $\psi_c$                      | [-]                  | 1,0                     |     |     |
| Increasing factor for C40/50                                    |                               |                      |                         |     |     |
| Increasing factor for C50/60                                    |                               |                      |                         |     |     |
| Installation factors for category I1 <sup>1)</sup>              | $\gamma_{inst}$               | [-]                  | 1,0                     |     |     |
| Installation factors for category I2 <sup>1)</sup>              |                               |                      | 1,2                     |     |     |

<sup>1)</sup> In the absence of other national regulation

**Table C13: Characteristic values shear resistance load for threaded rod for seismic performance category C1.**

| Size                         |                               |      | M12                     | M16 | M20 |
|------------------------------|-------------------------------|------|-------------------------|-----|-----|
| <b>Steel failure</b>         |                               |      |                         |     |     |
| Characteristic resistance    | $V_{Rk,s,eq,C1}$              | [kN] | $0,7 \times V_{Rk,s}^0$ |     |     |
| Partial factor <sup>1)</sup> | $\gamma_{Ms,V}$ <sup>1)</sup> | [-]  | See Annex C1 – Table C1 |     |     |

<sup>1)</sup> In the absence of other national regulation

**Table C14: Reduction factor for annular gap.**

| <b>Reduction factor for annular gap</b> |                |     |     |  |  |
|---|----------------|-----|-----|--|--|
| Without annular gap filling             | $\alpha_{gap}$ | [-] | 0,5 |  |  |
| With annular gap filling                | $\alpha_{gap}$ | [-] | 1,0 |  |  |

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**  
Characteristic resistance under tension and shear loads for threaded rod  
for seismic action category C1

**Annex C8**  
of European  
Technical Assessment  
ETA-09/0140

**Table C15: Characteristic values tension resistance load for threaded rod for seismic performance category C2.**

| Size  |                               |                      | M12                     | M16 |
|---|-------------------------------|----------------------|-------------------------|-----|
| <b>Steel failure</b>  |                               |                      |                         |     |
| Characteristic resistance                                       | $N_{Rk,s,eq,C2}$              | [kN]                 | $1,0 \times N_{Rk,s}$   |     |
| Partial factor <sup>1)</sup>                                    | $\gamma_{Ms,N}$ <sup>1)</sup> | [-]                  | See Annex C1 – Table C1 |     |
| <b>Combined pull-out and concrete cone failure</b>              |                               |                      |                         |     |
| Characteristic bond resistance temperature range -40°C / +40°C  | $\tau_{Rk,eq,C2}$             | [N/mm <sup>2</sup> ] | 1,6                     | 1,7 |
| Characteristic bond resistance temperature range -40°C / +80°C  | $\tau_{Rk,eq,C2}$             | [N/mm <sup>2</sup> ] | 1,2                     | 1,2 |
| Characteristic bond resistance temperature range -40°C / +120°C | $\tau_{Rk,eq,C2}$             | [N/mm <sup>2</sup> ] | 0,6                     | 0,7 |
| Increasing factor for C30/37                                    | $\psi_c$                      | [-]                  | 1,0                     |     |
| Increasing factor for C40/50                                    |                               |                      |                         |     |
| Increasing factor for C50/60                                    |                               |                      |                         |     |
| Installation factors for category I1 <sup>1)</sup>              | $\gamma_{inst}$               | [-]                  | 1,0                     |     |
| Installation factors for category I2 <sup>1)</sup>              |                               |                      | 1,2                     |     |

<sup>1)</sup> In the absence of other national regulation

**Table C16: Characteristic values shear resistance load for threaded rod for seismic performance category C2.**

| Size                            |                               |      | M12                      | M16                      |
|---------------------------------|-------------------------------|------|--------------------------|--------------------------|
| <b>Steel failure</b>            |                               |      |                          |                          |
| Characteristic shear resistance | $V_{Rk,s,eq,C2}$              | [kN] | $0,53 \times V_{Rk,s}^0$ | $0,46 \times V_{Rk,s}^0$ |
| Partial factor <sup>1)</sup>    | $\gamma_{Ms,V}$ <sup>1)</sup> | [-]  | See Annex C1 – Table C1  |                          |

<sup>1)</sup> In the absence of other national regulation

**Table C17: Reduction factor for annular gap.**

| Reduction factor for annular gap |                |     |     |  |
|----------------------------------|----------------|-----|-----|--|
| Without annular gap filling      | $\alpha_{gap}$ | [-] | 0,5 |  |
| With annular gap filling         | $\alpha_{gap}$ | [-] | 1,0 |  |

**Table C18: Displacements for tensile and shear load for seismic performance category C2 - threaded rod.**

| Size  |                            |      | M12  | M16  |
|---|----------------------------|------|------|------|
| <b>Displacements for tensile and shear load for seismic performance category C2</b> |                            |      |      |      |
| Displacement in tensile at damage limitation states                                 | $\delta_{N,eq,seis}$ (DLS) | [mm] | 0,20 | 0,23 |
| Displacement in tensile at ultimate limit state                                     | $\delta_{N,eq,seis}$ (ULS) | [mm] | 0,33 | 1,04 |
| Displacement in shear at damage limitation states                                   | $\delta_{V,eq,seis}$ (DLS) | [mm] | 2,01 | 0,70 |
| Displacement in shear at ultimate limit state                                       | $\delta_{V,eq,seis}$ (ULS) | [mm] | 4,68 | 2,12 |

**BOSSONG BCR V PLUS,  
BOSSONG BCR V PLUS-W and BOSSONG BCR V PLUS-T**

**Performances**  
Characteristic resistance under tension and shear loads for threaded rod  
for seismic performance category C2

**Annex C9**  
of European  
Technical Assessment  
ETA-09/0140